

# HOT WORK TOOL STEELS

## Application Segments

Hot Work

## Available Product Variants

Long Products

## Product Description

BÖHLER W722 VMR is not a classic hot work tool steel, but an ultra-high strength maraging steel. Compared to quenched and tempered steels, the material generates its high strength not through a hardened and tempered martensitic structure with a high carbon content and secondary hardening carbides, but through the precipitation of intermetallic phases from a tough nickel martensitic matrix. BÖHLER W722 VMR corresponds to material number 1.2709 (X3NiCoMoTi18-9-5) and has proven to be ideally suited for many tool steel applications in cold and hot work up to 450 °C. The Steel also is available as powder material for metal-3D-printing under the brand name BÖHLER W722 AMPO.

## Process Melting

VIM + VAR

## Applications

- > Extrusion
- > Fasteners, Bolts, Nuts
- > High Pressure Die-Casting
- > Injection Molding
- > General Components for Mechanical Engineering
- > Tool Holders (milling, drilling, turning & chucks)

## Technical data

Material designation	
1.2709	SEL

## Chemical composition (wt. %)

C	Si	Mn	Mo	Ni	Co	Ti
≤ 0,03	≤ 0,10	≤ 0,15	4,90	18,00	9,30	1,10

## Delivery condition

Solution annealed	
Hardness (HB)	max. 353

## Heat treatment


### Solution annealing

Temperature	820 °C	1 hour air, gas
-------------	--------	-----------------

### Precipitation hardening

Temperature	490 °C	6 hours air
-------------	--------	-------------

## Ageing chart

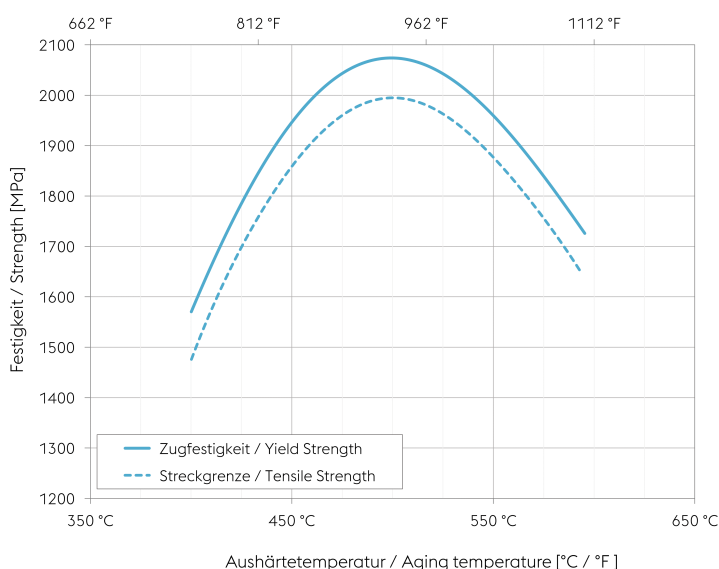

### Aging:

Solution annealed 820°C (1508°F) / 1 hour / air  
Aging time: 3 hours

For maximum hardness there is also the possibility to age 6 hours at 490°C (914°F).

## Physical Properties

Temperature (°C)	20
Density (kg/dm <sup>3</sup> )	8.1
Thermal conductivity (W/(m.K))	21
Specific heat (kJ/kg K)	0.42
Spec. electrical resistance (Ohm.mm <sup>2</sup> /m)	0.42
Modulus of elasticity (10 <sup>3</sup> N/mm <sup>2</sup> )	200

## Thermal Expansions between 20°C | 68°F and ...

Temperature (°C)	100	200	300	400	500
Thermal expansion (10 <sup>-6</sup> m/(m.K))	10.3	10.7	11	11.3	11.6

---

If other available product variants are listed in addition to long products, please note that these may differ in terms of melting process, technical data, delivery and surface condition as well as available product dimensions. For mandatory technical specifications, other requirements and dimensions, please contact our regional voestalpine BÖHLER sales companies. The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.

**voestalpine BÖHLER Edelstahl GmbH & Co KG**  
Mariazeller Straße 25  
8605 Kapfenberg, AT  
T. +43/50304/20-0  
E. [info@bohler-edelstahl.at](mailto:info@bohler-edelstahl.at)  
<https://www.voestalpine.com/bohler-edelstahl/de/>

**voestalpine**  
ONE STEP AHEAD.